



# NEW VARIANT OF THE STRUCTURE OF THE $\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$ INTERMETALLIC COMPOUND

V.V. Pavlyuk<sup>1</sup>, G.S. Dmytriv<sup>1</sup>, O.I. Bodak<sup>1</sup>, J. Stepien-Damm<sup>2</sup>

<sup>1</sup>Inorganic Chemistry Department, Ivan Franko Lviv National University, Lviv, Ukraine

<sup>2</sup>Institute of Low Temperature and Structure Research, Wroclaw, Poland

## Abstract

Existence of compound with wide homogeneity range along isoconcentrate of 0.33 atomic part of Li  $\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$  have been confirmed and composition and lattice periods have been determined by powder diffraction (powder diffractometer DRON-2.0,  $\text{FeK}\alpha$ -radiation):  $a = 1.4017(3) \div 1.3904(3)$  nm; increasing of lattice period with changing  $x$  from 0 to 0.06 part of lithium is 0.0023 nm.

The crystal structure of  $\text{LiZnAl}$  have been solved by the single-crystal X-ray analysis (KM-4 automatic diffractometer,  $\text{MoK}\alpha$ -radiation with graphite monochromator,  $\omega/\theta$  scan mode,  $4^\circ \leq 27^\circ \leq 70^\circ$ , number of unique (hkl) - 434,  $R = 0.044$ ). This compound crystalized in  $\text{LiCuSi}$  structure type, space group  $Im\bar{3}$ .

For statistical mixture of Zn and Al in general characteristic icosahedral coordination of polyhedrons (coordinating numbers 11 for M3, 12 for M2 and M4 and 14 for M1). For Li atoms characteristic more complicated polyhedrons with coordinating numbers 15 for Li1 and 16 for Li2 and Li3.

## 1. Introduction

First information about the existence of the compound with a wide homogeneity range along the isoconcentrate of 33.3 at.% of Li in the Li-Zn-Al system was presented in [1]. The  $\text{Mg}_{32}(\text{Zn},\text{Al})_{49}$  structure type for this compound with approximate composition  $\text{LiZn}_{0.5-1.3}\text{Al}_{1.5-0.7}$  was proposed in [2].

We have investigated Li-Zn-Al system in whole concentration range at 470 K and confirmed existence of this compound. Results of our research elaborated the homogeneity range for this compound:

$\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$ . We have also refined its crystal structure in  $\text{LiCuSi}$  structure type by the X-ray single crystal method.

## 2. Experimental

Alloys of the Li-Zn-Al system were prepared by arc-melting pieces of the pure metals (lithium with a purity 98.2 wt.%, zinc with a purity 99.98 wt.%, aluminium with a purity 99.99 wt.%) in the argon atmosphere. The alloys were annealed at 470 K for 400 hours in a tantalum containers in an evacuated quartz ampoules and quenched in a cold water.

Powder patterns were obtained by powder diffractometer DRON-2.0 ( $\text{FeK}\alpha$ -radiation,

$20^\circ \leq \theta \leq 100^\circ$ ,  $2^\circ/\text{min}$  speed of scanning). Lattice parameters were calculated using LATCON program.

The X-ray intensities data were collected by a Kuma-Diffraction KM-4 four-circle single crystal diffractometer using graphite-monochromatized  $\text{MoK}\alpha$  radiation ( $\omega/\theta$  scan mode,  $4^\circ \leq 2\theta \leq 70^\circ$ ,  $0.03-0.1^\circ/\text{min}$  speed of scanning). Structure was solved by the direct method and refined by the full-matrix least squares method using the SHELXL program [3].

## 3. Results and Discussion


The main reason of the present investigation was the conclusion of author [2] on the belonging of the crystal structure of the  $\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$  compound to the  $\text{Mg}_{32}(\text{Zn},\text{Al})_{49}$  structure type which was based only on the comparison of Debye-Scherrer photographs (camera RKD-57.3) of compounds with composition from concentration interval  $\text{LiZn}_{0.5-1.3}\text{Al}_{1.5-0.7}$  with photograph of early investigated compound  $\text{Li}_3\text{CuAl}_5$ , without refinement of the structure. Boundaries of homogeneity range and change of lattice parameters in it we calculated using powder patterns. Change of the lattice parameters  $a$  of  $\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$  along the isoconcentrate 33.3 at.% of Li is  $1.4017(3)1.3904(3)$  nm and the increase of lattice parameters  $a$  with change of  $x$  from 0 to 0.06 is 0.0023 nm.

For the refinement of crystal structure of


$\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$  compound we investigated single crystal, obtained from alloy with composition  $\text{LiZnAl}$ , by the Kuma-Diffraction KM-4 four-circle single crystal diffractometer. Structure was solved in  $Im\bar{3}$  space group, but as  $\text{LiCuSi}$  structure type in contrast to  $\text{Mg}_{32}(\text{Zn},\text{Al})_{49}$  structure type proposed by [2]. Our model of crystal structure of the  $\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$  compound differs from the model [2] by two aspects: first, the site 2(a) is vacant (in

Table 1. Atomic parameters of the  $\text{LiZnAl}$  compound

Atom	Site	x	y	z	$B_{\text{eq}}$
M1(13%Zn+87%Al)	12(e)	1/2	0.096(1)	0	0.375
M2(89%Zn+11%Al)	24(g)	0	0.312(2)	0.177(2)	0.460
M3(58%Zn+42%Al)	24(g)	0.154(1)	0.094(2)	0	0.407
M4(31%Zn+69%Al)	48(h)	0.406(2)	0.191(2)	0.158(2)	0.420
Li1	12(e)	1/2	0	0.196(1)	0.489
Li2	16(f)	0.187(1)	0.187(1)	0.187(1)	0.489
Li3	24(g)	0	0.118(2)	0.302(2)	0.450

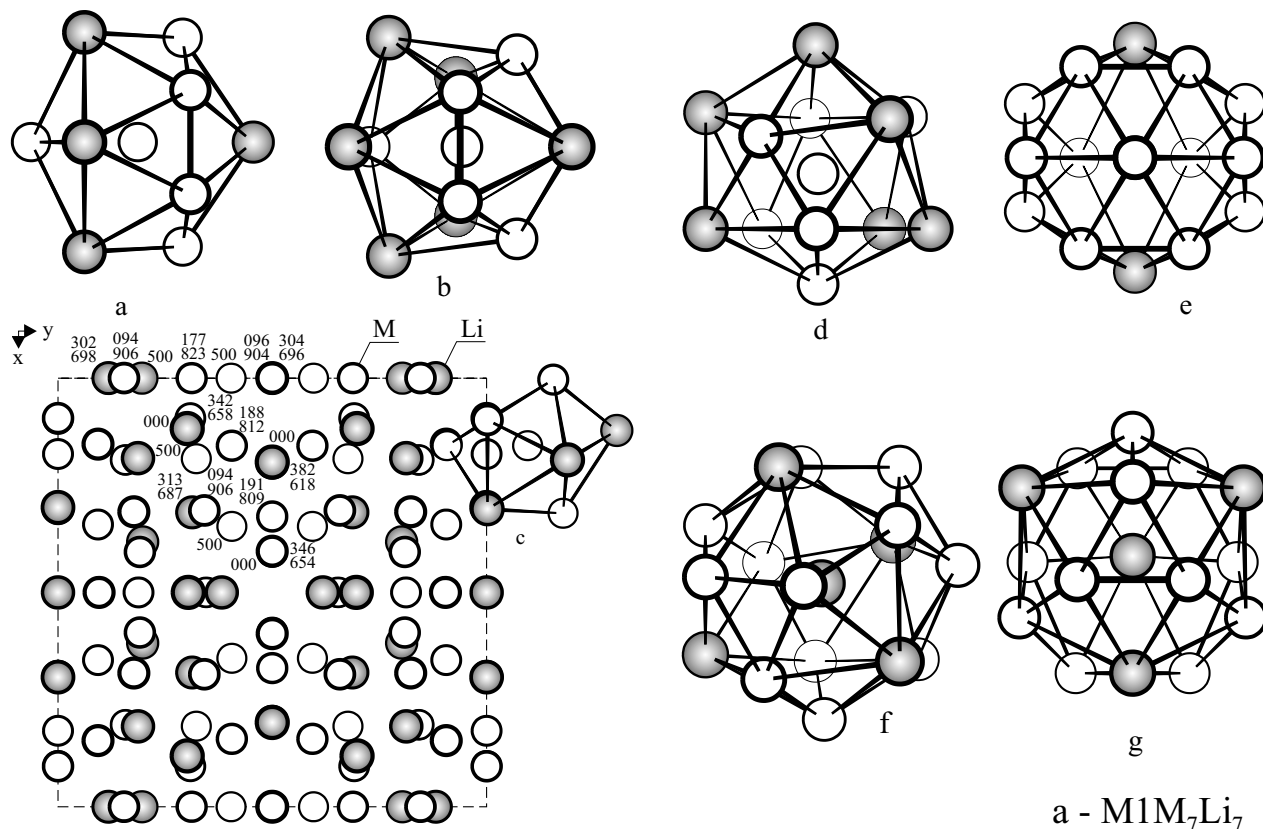

**Fig.1** The projection of the unit cell of the  $Li_{1+x}Zn_{0.5-1.5}Al_{1.5-0.5}$  compound on the X-Y plane and the coordination polyhedra of the atoms.

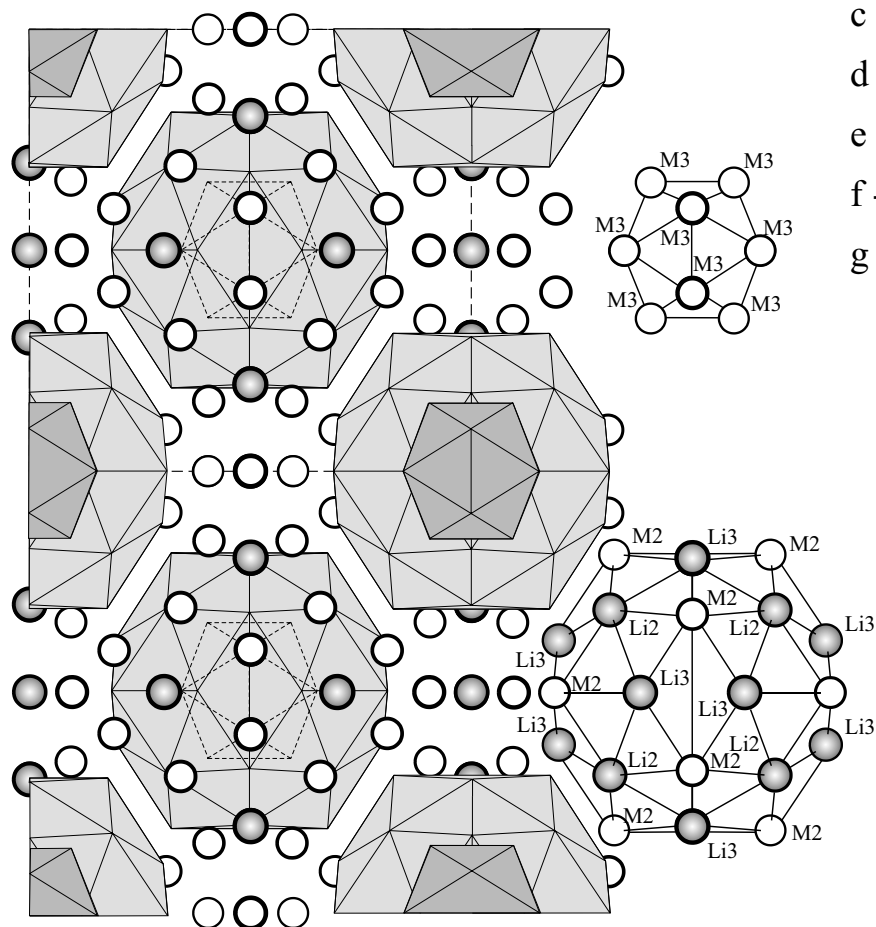

**Fig.2.** Packing of 32-vertices polyhedron complexes formed from M2, M3, Li2 and Li3 atoms around vacancies in 0 0 0 and  $\frac{1}{2} \frac{1}{2} \frac{1}{2}$  positions in the structure of the  $Li_{1+x}Zn_{0.5-1.5}Al_{1.5-0.5}$  compound.

**Table 2.** Interatomic distances and C.N. in the LiZnAl structure

---



---



---

model [2] this site is occupied by Al atoms); second, one of the sites 12(e) is occupied by Li atoms (in model [2] both sites 12(e) are occupied by mixtures of Zn and Al atoms statistically). Finally crystal structure is refined in isotropic approximation with  $F(hkl) > 3\sigma(F)$  to  $R=0.044$  (number of unique  $(hkl)$  - 434). Atomic parameters obtained after re-

fining are presented in the Table 1. Atomic coordinates are transformed in standard setting according to [4] (Table 1). Interatomic distances and coordination numbers (C.N.) in the structure of LiZnAl compound are presented in the Table 2.

The projection of the unit cell on the X-Y plane and the coordination polyhedra of the atoms are shown in Fig 1. Statistical mixture of Zn and Al atoms (atoms with minimal size in this structure) are characterized by icosahedral coordination. The coordination polyhedra of M2 and M4 are distorted icosahedra  $[\text{M2M}_6\text{Li}_6]$  and  $[\text{M4M}_6\text{Li}_6]$ , the coordination polyhedron of M3 is defected icosahedron  $[\text{M3M}_6\text{Li}_5]$  (vacancy in 2(a) site in icosahedron sphere). The coordination polyhedron of M1 has 14 vertices -  $[\text{M1M}_7\text{Li}_7]$ . There are three complicated coordination polyhedra of lithium atoms: one with 15-vertices  $[\text{Li1M}_{13}\text{Li}_2]$  and two with 16-vertices:  $[\text{Li2M}_{12}\text{Li}_4]$  and  $[\text{Li3M}_{12}\text{Li}_4]$ .

The crystal structure of  $\text{Li}_{1+x}\text{Zn}_{0.5-1.5}\text{Al}_{1.5-0.5}$  compound can be described as a packing of 32-vertices polyhedron complexes formed from M2, M3, Li2 and Li3 atoms around vacancies in 0 0 0 and  $\frac{1}{2} \frac{1}{2} \frac{1}{2}$  positions and surrounded by the net from the M1, M4 and Li1 atoms (Fig. 2). The regular icosahedron from M3 atoms is in the a center of the complex. Li3 atoms are situated in opposite to every from 12 icosahedron edges which is in the form of isosceles triangles, Li2 atoms are situated in opposite to every from 8 icosahedron edges which is in the form of equilateral triangles, M2 atoms are situated in opposite to icosahedron vertices.

## References

1. T.A.Badajeva, P.Ya.Saldau., *J. General Chem.*, **13** (1943) 643-660.
2. E.E.Cherkashyn, P.I.Krypiakevich, G.I.Oleksiv, *Crystallography*, **8** (1963) 846-851.
3. G.M.Sheldrick, SHELXL-93, a Program for Refining Crystal Structures. Göttingen 1993.
4. International Tables for X-ray Crystallography. Birmingham 1965.